

NOTIZEN

The Anisotropy Function $\eta(T)$ in Al-Cu and Al-Zn Alloys

Constantin Papastaikoudis

Nuclear Research Center "Dimocritos", Aghia Paraskevi,
Athens, Attiki, Greece

(Z. Naturforsch. **32a**, 327–328 [1977];
received February 7, 1977)

The anisotropy function $\eta(T)$ for Al-Cu and Al-Zn alloys is determined experimentally and compared with the theoretical results of Kagan and Zhernov.

Recent resistivity measurements on Al-Zn^{1, 2} and Al-Cu³ alloys have shown that the deviation $\Delta(c, T)$ from Matthiessen's rule is positive at low temperatures and increases with T , passing through a maximum at intermediate temperatures. At high temperatures, in the Al-Zn alloys investigated by Kawata et al.¹ the deviation increases approximately linearly with T , while in the Al-Cu alloys investigated by Papastaikoudis et al.² it decreases linearly with T . For the Al-Cu alloys the deviation remains almost constant³.

It is the main feature of these measurements that the maximum of $\Delta(c, T)$ shifts with Zn and Cu concentration. In Al-Cu alloys it has been shown³ that the temperature T_{\max} , corresponding to the maximum of the deviation, follows very well a $c^{1/5}$ law. The same behaviour is also followed by the Al-Zn system as shown in Fig. 1, where the T_{\max} is plotted as a function of concentration c in a log-log plot.

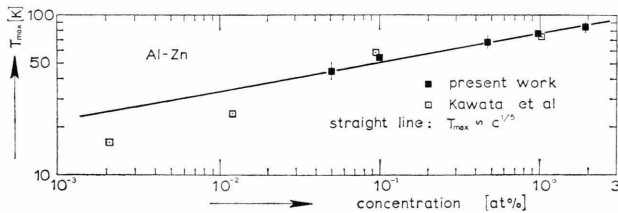


Fig. 1. T_{\max} as a function of the solute concentration c .

The $c^{1/5}$ law for T_{\max} was initially explained by Kagan and Zhernov⁴ who in their calculation have taken into account the effect of the anisotropy of the electron-phonon scattering. This anisotropy is connected with Umklapp processes and the anisotropy of the vibrational spectrum of metals. In this case, and with the assumption that the Fermi surface is spherical, they have found that the resistivity

of a pure metal has the form

$$\varrho_p'(T) = \varrho_p(T) [1 - \eta(T)], \quad (1)$$

where $\varrho_p(T)$ is the resistivity of the pure metal in the first (isotropic) approximation and the factor $\eta(T)$ is a function of T due to the anisotropy. In the presence of small amounts of impurities in the metal, they found an expression for the departure from Matthiessen's rule $\Delta(c, T)$, which has the form

$$\Delta'(c, T) = \Delta(c, T) + \varrho_p(T) \eta(T) \left[1 - \frac{1}{1 + cR/P(T)} \right]. \quad (2)$$

The quantity $\Delta(c, T)$ was calculated by the use of an isotropic distribution function, R is an integral arising from the elastic scattering of the electrons from foreign atoms and $P(T)$ is an integral associated with the electron-phonon scattering in the pure metal. In the region of low temperatures the ratio $cR/P(T)$ is large, while at high temperatures it is small. In the intermediate temperature range for which $P(T) \sim cR$, that is when $\varrho_p(T)$ is comparable in magnitude with the residual resistivity ϱ_0 , the magnitude of the impurity resistivity itself turns out to be large, namely

$$\Delta(c, T)/\varrho_0(c) \sim \eta(T). \quad (3)$$

Kagan and Zhernov have defined a characteristic temperature \tilde{T} for $P(T) = cR$, which, due to the proportionality of $P(T)$ to T^5 obeys the relation

$$\tilde{T} \sim c^{1/5}. \quad (4)$$

\tilde{T} is nearly equal to the temperature T_{\max} corresponding to the maximum of the deviation.

In Fig. 2 the dashed curve shows the theoretically calculated factor $\eta(T)$ as a function of T/Θ_D

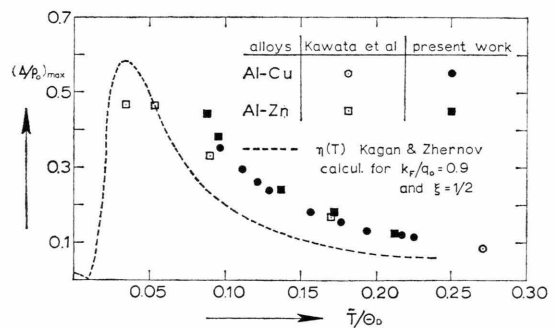


Fig. 2. $(\Delta/\varrho_0)T_{\max}$ against \tilde{T}/Θ_D , together with the calculated $\eta(T)$ function.



Dieses Werk wurde im Jahr 2013 vom Verlag Zeitschrift für Naturforschung in Zusammenarbeit mit der Max-Planck-Gesellschaft zur Förderung der Wissenschaften e.V. digitalisiert und unter folgender Lizenz veröffentlicht: Creative Commons Namensnennung-Keine Bearbeitung 3.0 Deutschland Lizenz.

Zum 01.01.2015 ist eine Anpassung der Lizenzbedingungen (Entfall der Creative Commons Lizenzbedingung „Keine Bearbeitung“) beabsichtigt, um eine Nachnutzung auch im Rahmen zukünftiger wissenschaftlicher Nutzungsformen zu ermöglichen.

This work has been digitalized and published in 2013 by Verlag Zeitschrift für Naturforschung in cooperation with the Max Planck Society for the Advancement of Science under a Creative Commons Attribution-NoDerivs 3.0 Germany License.

On 01.01.2015 it is planned to change the License Conditions (the removal of the Creative Commons License condition "no derivative works"). This is to allow reuse in the area of future scientific usage.

for the case $k_F/q_0=0.9$. The parameter ξ , characterizing the phonon spectrum anisotropy was set⁴ at $1/2$. Θ_D is the Debye temperature, k_F is the radius of the Fermi sphere and $q_0=\pi \cdot b_{\min}$, where b_{\min} is the nearest vector of the reciprocal lattice. The same figure also shows our experimental values of $\Delta(c,T)/\varrho_0$ for the Al-Cu and Al-Zn alloy systems, which are taken at T_{\max} , together with those of Kawata et al.¹. A comparison between the calculated $\eta(T)$ -curve and the experimental $\Delta(c,T)/\varrho_0$ results shows that there is relatively a good agree-

ment. This agreement points out that the calculation of Kagan and Zhernov⁴ provides an explanation for the observed maximum of the deviation from Matthiessen's rule at intermediate temperatures and its shift with the concentration of the impurities.

Acknowledgements

The author wishes to thank Prof. G. Vourvopoulos for careful reading of the manuscript.

¹ S. Kawata and T. Kito, J. Phys. Soc. Japan **39**, 684 [1975].

² C. Papastaikoudis, K. Papathanasopoulos, and E. Rocofyllou, J. Phys. F: Metal Phys. **6**, 409 [1976].

³ C. Papastaikoudis, K. Papathanasopoulos, E. Rocofyllou, and W. Tselfes, Phys. Rev. B **14**, 3394 [1976].

⁴ Yu. Kagan and A. P. Zhernov, Zh. Eksp. Teor. Fiz. **60**, 1832 [1971] [Sov. Phys. — JETP **33**, 990 (1971)].