

## On the Thermal Behaviour of Long-chain Potassium *n*-alkanoates

P. Ferloni, G. Spinolo, M. Zangen \*  
and P. Franzosini

Centro di studio per la termodinamica ed elettrochimica dei sistemi salini fusi e solidi del C.N.R. c/o Istituto di Chimica-Fisica e di Elettrochimica della Università, Pavia (Italy)

(Z. Naturforsch. **32a**, 329–331 [1977];  
received February 2, 1977)

Differential scanning calorimetry was performed between 110 K and the isotropic melt region on potassium *n*-alkanoates from octanoate to dodecanoate. Clearing, melting and (crystalline) solid state transition temperatures and heat effects were measured. In the higher homologues the occurrence of phases (likely “waxy”) intermediate between crystalline solid and mesomorphic liquid could also be argued. The phase relationships are discussed in comparison with some roentgenographic and microscopic results of previous authors.

### 1. Introduction

The phase relationships in the even K *n*-alkanoates for which  $8 \leq n_C \leq 18$  ( $n_C$ : number of C atoms) had been investigated: (i) from room temperature up to the isotropic melt region by Gallot and Skoulios<sup>1</sup> (X-ray diffraction patterns); (ii) between  $\sim 450$  and  $\sim 670$  K by Baum et al.<sup>2</sup> (visual observation at the heating stage polarizing microscope). The latter took also into account  $KC_9$  \*\*.

Both agreed on the fact that each salt could exist as a mesomorphic liquid (“neat” phase<sup>2</sup> of a “labile lamellar” structure<sup>1</sup>) in a temperature region the lower limit of which ranged between  $\sim 560$  K in the case of  $KC_8$  and  $\sim 540$  K in the case of  $KC_{18}$ . Far diverging values were however attributed to the upper limits.

Moreover, at  $T < 540$  K Gallot and Skoulios<sup>1</sup> identified: (i) in  $KC_8$ ,  $KC_{10}$  two different, and in  $KC_{12}$ ,  $KC_{14}$ ,  $KC_{16}$ ,  $KC_{18}$  three different “crystalline lamellar” (CL) phases; (ii) in  $KC_{14}$  several “disc”, and in  $KC_{16}$ ,  $KC_{18}$  several “ribbon” structures.

Anyway, the mentioned discrepancies, the poor information on phase relationships in odd homologues, and the absence of thermal data on any of the

above transitions suggested as worthy a calorimetric re-investigation of this salt family. The present paper deals with the  $KC_8 - KC_{12}$  series.

### 2. Experimental

C. Erba RPE metallic potassium, and Fluka puriss. *n*-octanoic ( $\geq 99.5$  mole %), *n*-nonanoic ( $> 99$ ), *n*-decanoic ( $\geq 99$ ), *n*-hendecanoic ( $> 99.5$ ), *n*-dodecanoic ( $> 99.5$ ) acids were used as starting materials.

The alkanoates were prepared by reaction of finely divided K under toluene with the proper acid in toluene solution. When no more  $H_2$  escaped, some anhydrous ethanol was added to dispose of any rest of unreacted metal. After filtration, the salts were repeatedly washed with acetone and finally re-crystallized from 2-propanol.

The transition (tr) temperatures ( $T_{tr}/K$ ) and enthalpies ( $\Delta H_{tr}/kcal\ mole^{-1}$ ) were measured by means of a Perkin Elmer Mod. DSC-2 differential scanning calorimeter (for details on procedure see Ref. <sup>3</sup>). Sealed Al containers were employed.

### 3. Results and Discussion

3.1. Let us first consider the field of existence of the “neat” phase (see Table 1 and Figure 1).

Table 1. Clearing and fusion.

salt	tr	this work <sup>a</sup>		Ref. 1 <sup>b</sup>		Ref. 2 <sup>c</sup>	
		$T_{tr}$ K	$\Delta H_{tr}$ kcal mole <sup>-1</sup>	$T_{tr}$ K		$T_{tr}$ K	
$KC_8$	Cl	712 $\pm$ 2	0.63 $\pm$ 0.02	652		> 673	
	F	560.6 $\pm$ 0.8	4.38 $\pm$ 0.05	551		564	
$KC_9$	Cl	707.4 $\pm$ 0.8	0.59 $\pm$ 0.03	—		> 673	
	F	549.1 $\pm$ 0.8	3.54 $\pm$ 0.10	—		555	
$KC_{10}$	Cl	696	0.50 $\pm$ 0.02	649		> 673	
	F	544	2.91 $\pm$ 0.06	547		550	
$KC_{11}$	Cl	691.4 $\pm$ 0.8	0.44 $\pm$ 0.01	—		—	
	F	541 $\pm$ 2	2.87 $\pm$ 0.04	—		—	
$KC_{12}$	Cl	679.2 $\pm$ 0.5	0.44 $\pm$ 0.01	647		668	
	F	540.8 $\pm$ 0.5	2.83 $\pm$ 0.06	545		546	

<sup>a</sup> DSC

<sup>b</sup> X-ray diffraction patterns.

<sup>c</sup> Heating stage polarizing microscope.

According to the recorded DSC traces, the clearing temperature ( $T_{Cl}/K$ , at which the mesomorphic liquid changes into isotropic) progressively decreases from  $\sim 712$  to  $\sim 679$  K as  $n_C$  increases from 8 to 12: the figures given in Ref. 1 are therefore to be considered by  $\sim 60$  to  $\sim 30$  K too low, whereas the

\* On sabbatical leave from Soreq Nuclear Center, Yavne, Israel. A grant from the Italian National Research Council is gratefully acknowledged.

\*\* For the sake of simplicity, potassium *n*-octanoate, *n*-nonanoate, . . . , are here briefly indicated as  $KC_8$ ,  $KC_9$ , . . . , respectively.

Reprint requests to Prof. Paolo Franzosini, Istituto di Chimica-Fisica e di Elettrochimica della Università, Viale Taramelli 16, I-27100 Pavia (Italy).



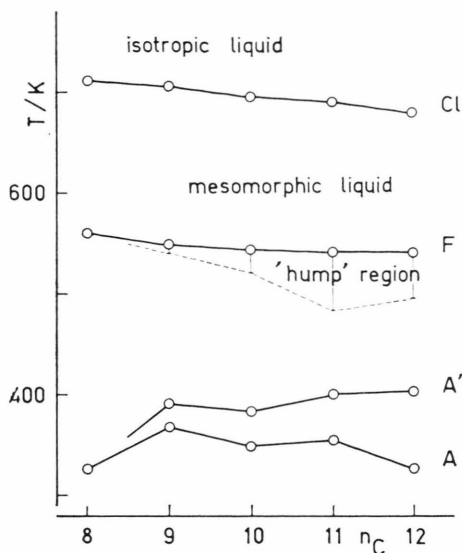


Fig. 1. Phase transition temperatures in the  $KC_8$ – $KC_{12}$  series.

qualitative remark by Baum et al.<sup>2</sup> that  $T_{Cl}$  exceeds 673 K when  $8 \leq n_C \leq 10$  remains valid.

A satisfactory convergency exists on the contrary between present and previous results on fusion temperatures ( $T_F/K$ , intended here as the lower limits

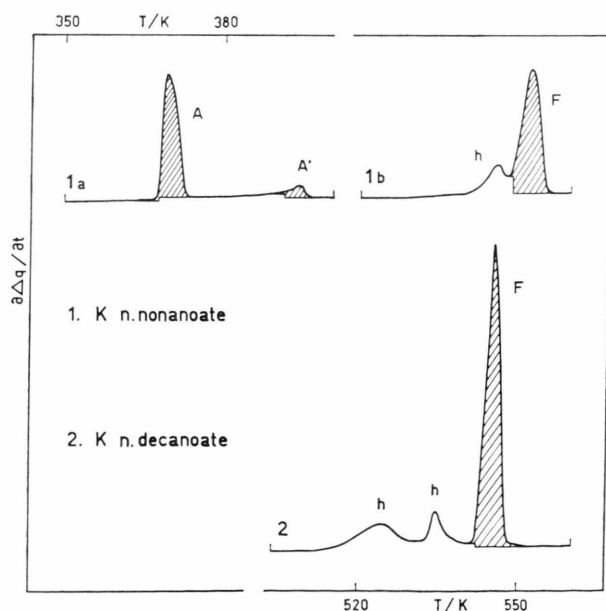


Fig. 2. DSC traces taken (in the same operational conditions) on a  $KC_9$  and a  $KC_{10}$  sample. Curve 1 a: sstr's A and A' in  $KC_9$ ; curve 1 b: "hump" (h) and fusion peak in  $KC_9$ ; curve 2: "humps" and fusion peak in  $KC_{10}$ . Hatched areas taken into account for  $\Delta H_{tr}$  calculations.

of the "neat" fields independently of the nature of the phase in equilibrium – at  $T_F$  – with the "neat" one in each alkanolate).

It is anyway to be said that DSC analysis allowed to record a unique peak only in the case of  $KC_8$ , whereas in the higher homologues the peaks to be attributed to fusion were always preceded by one or more "humps". Figure 2 shows a few examples of the latter, the nature of which may be tentatively explained as follows.

On one hand the already mentioned Gallot and Skoulios' ribbon or disc structures ("waxy" phases in the terminology by Baum et al.) were detected between  $T_F$  and ( $T_F$ -102), ( $T_F$ -85), ( $T_F$ -75) in  $KC_{18}$ ,  $KC_{16}$ ,  $KC_{14}$ , respectively, i.e., within temperature ranges becoming increasingly narrow as  $n_C$  decreases. On the other hand in the even homologues we took into account, "humps" were recorded between  $T_F$  and ( $T_F$ -46), ( $T_F$ -23) in  $KC_{12}$ ,  $KC_{10}$ , respectively, and were absent in  $KC_8$ . Now, should the above  $\Delta T$ 's be plotted vs  $n_C$  (see Fig. 3) the

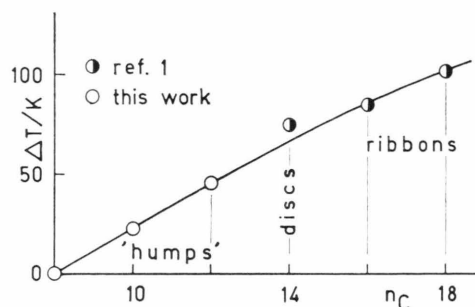


Fig. 3. Width of the "intermediate phases" region in even  $K n$ .alkanoates: for explanation see text.

Table 2. Solid state transitions.

salt		this work <sup>a</sup>		Ref. 1 <sup>b</sup>	
		tr	$\frac{\Delta H_{tr}}{K}$	tr	$\frac{T_{tr}}{K}$
$KC_8$	A	$326.6 \pm 0.1$	$2.26 \pm 0.05$	(CL) <sub>1</sub> – (CL) <sub>2</sub>	331
	A'	$390.5 \pm 0.4$	$0.32 \pm 0.03$	—	—
$KC_{10}$	A	$348.7 \pm 0.5$	$1.96 \pm 0.02$	(CL) <sub>1</sub> – (CL) <sub>2</sub>	350
	A'	$382.9 \pm 0.6$	$0.24 \pm 0.01$	—	—
$KC_{11}$	A	$355.0 \pm 0.6$	$3.56 \pm 0.06$	—	—
	A'	$400 \pm 2$	$0.66 \pm 0.05$	—	—
$KC_{12}$	A	$327.2 \pm 0.4$	$2.79 \pm 0.03$	(CL) <sub>1</sub> – (CL) <sub>2</sub>	328
	A'	$404 \pm 2$	$0.72 \pm 0.06$	(CL) <sub>2</sub> – (CL) <sub>3</sub>	408

<sup>a</sup> DSC

<sup>b</sup> X-ray diffraction patterns.

trend of the curve suggests that "waxy" phases intermediate between mesomorphic liquid and crystalline solid may exist (though having escaped to previous investigations) also in potassium *n*-alkanoates where  $n_C < 14$ , and vanish only when  $n_C = 8$ .

3.2. Coming to the crystalline solid field, DSC traces proved in each member of the  $KC_8-KC_{12}$  series the occurrence at  $320 < T_{tr} < 370$  of a solid state transition (sstr A, see Table 2) involving a heat effect at least as large as  $2 \text{ kcal mole}^{-1}$ . This transition too appears to be unique in  $KC_8$  only, whereas in each of the higher homologues it is accompanied by a sstr A', which occurs at  $380 < T_{tr} < 410$  and involves a remarkably smaller

heat effect ( $0.7 \text{ kcal mole}^{-1}$ , or less). An example of such twinning is shown in Figure 2.

As for the even homologues where  $8 \leq n_C \leq 12$  sstr's from  $(CL)_1$  to  $(CL)_2$  phases were already observed<sup>1</sup> at temperatures satisfactorily agreeing with the present  $T_A$ 's. Evidence for a further transition from a  $(CL)_2$  to a  $(CL)_3$  phase could however be obtained by Gallot and Skoulios only in  $KC_{12}$ : DSC analysis has now improved the picture showing the occurrence of a second sstr also in the three lower homologues  $KC_{11}$ ,  $KC_{10}$ ,  $KC_9$ .

3.3. Samples of  $KC_8-KC_{12}$  were scanned down to 110 K, but none was found to undergo any other sstr in this temperature region.

<sup>1</sup> B. Gallot and A. Skoulios, *Kolloid-Z., Z. Polymere*, **210**, 143 [1966].

<sup>2</sup> E. Baum, D. Demus, and H. Sackmann, *Wiss. Z. Univ. Halle XIX* '70, 37.

<sup>3</sup> P. Ferloni and P. Franzosini, *Gazz. Chim. Ital.* **105**, 391 [1975].