

## Evidence for Polymorphism within the So-called "Blue Phase" of Cholesteric Esters.

### II. Selective Reflection and Optical Rotatory Dispersion

K. Bergmann, P. Pollmann, G. Scherer,  
and H. Stegemeyer

Lehrstuhl für Physikalische Chemie, Gesamthochschule  
Paderborn

Z. Naturforsch. **34a**, 253–254 (1979);  
received December 19, 1978

In cholesteryl nonanoate the existence of two polymorphic forms of the so-called "blue phase" has been evidenced by selective reflection and optical rotatory dispersion measurements. The spectroscopic results indicate a discontinuous transition between the two phases.

Recently, we have reported [1] that the blue colour of the so-called "blue phase" (BP) of some cholesteryl esters originates from a selective reflection of circularly polarized light (SR) as described for the plane texture of cholesteric phases [2]. Additionally, within the wavelength region of SR an anomalous dispersion of optical rotatory power (ORD) has been found in the BP state [1]. According to the deVries theory of optical properties of cholesterics [2], the SR as well as the ORD results indicate that the BP state implies in some way a helical arrangement of the mesogenic molecules.

As described in Part I [3] the existence of two polymorphic BP states has been derived from calorimetric measurements. The aim of this paper is to investigate if the two different phases BP I and BP II give rise to different SR and ORD spectra. The SR spectra were measured in a Cary 17 I spectrophotometer with a Mettler FP 5 heating stage; the ORD spectra were scanned in a Jasco J 20 spectropolarimeter between quartz plates, sample thickness 25 or 12  $\mu\text{m}$ , respectively. As an example, we describe the results obtained in the case of cholesteryl nonanoate (CN):

On cooling the isotropic liquid state of CN, at 91.50 °C a sharp SR band occurs at  $\lambda_{\text{II}} = 404 \text{ nm}$ , which is shifted to 407 nm on further cooling down to 91.35 °C. At this temperature additionally a second SR band was observed at  $\lambda_{\text{I}} = 461 \text{ nm}$  (cf.

Figure 1). On decreasing the temperature the first SR peak at 407 nm vanishes whereas the second one remains and is shifted on further cooling to 494 nm at 91.05 °C. The ORD spectrum of CN exhibits an anomalous dispersion in the wavelength region of about 405 nm at temperatures  $91.50 > \vartheta > 91.35 \text{ °C}$ , whereas the region of anomalous ORD at  $\vartheta \leq 91.35 \text{ °C}$  is discontinuously shifted to about 465 nm (see Figure 1).

As the cholesteric state of CN has been found to exhibit a SR band at 352 nm [1] the two reflection peaks described above are to be attributed to two different BP states of CN. At the transition temperature  $\vartheta = 91.35 \text{ °C}$  the polymorphic states BP I and BP II coexist as can be seen from the simultaneous occurrence of two SR bands (see Figure 1). From the SR measurements the following phase transition temperatures (in °C) could be derived for CN and correspond with the DSC results (see Part I [3]):

$$\text{chol-91.05}^\circ\text{-BP I-91.35}^\circ\text{-BP II-91.50}^\circ\text{-isotr}$$

The relative accuracy of the temperature measurements is better than 0.05 °C.

At temperatures below 91.05 °C the BP I state can be supercooled, which is accompanied by a bathochromic shift of  $\lambda_{\text{I}}$  up to 540 nm. As mentioned before [1], in the supercooled state  $\lambda_{\text{I}}$  is dependent on the experimental conditions (e.g. cooling rates). Starting from a focal-conic texture of the CN

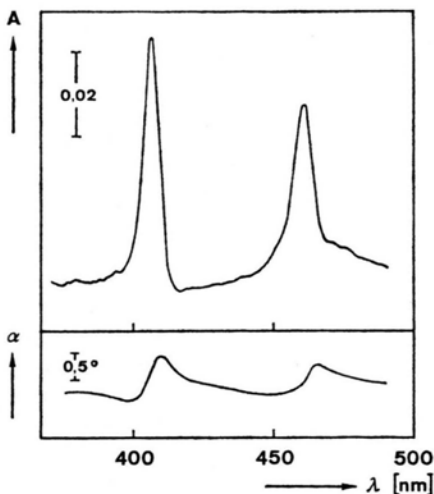


Fig. 1. Selective light reflection  $A(\lambda)$  and optical rotatory dispersion  $\alpha(\lambda)$  of CN at the transition temperature BP I  $\leftrightarrow$  BP II  $\vartheta = 91.35 \text{ °C}$ . Sample thickness: 25  $\mu\text{m}$  (SR); 12  $\mu\text{m}$  (ORD).

Reprints requests to Prof. Dr. H. Stegemeyer, Lehrstuhl für Physikalische Chemie, Gesamthochschule Paderborn, Postfach 1621, D-4790 Paderborn.

0340-4811 / 79 / 0200-0253 \$ 01.00/0

cholesteric state, on increasing the temperature the SR bands  $\lambda_I$  and  $\lambda_{II}$  appear at the same transition temperatures as mentioned above. As the reflected light within the SR bands is found to be left-circularly polarized in the BP I as well as in the BP II state, the screw sense of the molecular helical arrangement is left-handed as in the corresponding cholesteric state of CN [1].

In cholesteryl myristate also two different SR bands could be detected indicating two polymorphic BP states in agreement with the similar behaviour to CN found by calorimetric measurements [3]. These results will be published elsewhere.

Our spectrophotometric results confirm the existence of two polymorphic BP states which are

thermodynamically stable in a very small temperature range. The discontinuous shift of the SR band at 91.35 °C indicates a first order phase transition BP I  $\rightleftharpoons$  BP II in agreement with finite values of the transition enthalpy (cf. Part I [3]). The selective reflection of circularly polarized light as well as the anomalous dispersion of optical rotatory power support the suggestion of some chiral molecular arrangement within these two BP phases.

This work has been supported by the Deutsche Forschungsgemeinschaft and the Ministerium für Wissenschaft und Forschung des Landes Nordrhein-Westfalen.

[1] K. Bergmann and H. Stegemeyer, Ber. Bunsenges. Phys. Chem. **82**, 1309 (1978).

[2] H. deVries, Acta Cryst. **4**, 219 (1951).

[3] K. Bergmann and H. Stegemeyer, Z. Naturforsch. **34**, 251 (1979).