

On the Structural Evolution of the Amorphous $\text{Al}_{75}\text{Cu}_{15}\text{V}_{10}$ Alloy to the Icosahedral Phase

E. Matsubara, Y. Waseda

Research Institute of Mineral Dressing
and Metallurgy (SENKEN),
Tohoku University, Sendai 980, Japan

A. P. Tsai, A. Inoue, and T. Masumoto

Institute of Materials Research, Tohoku University,
Sendai 980, Japan

Z. Naturforsch. **43a**, 505–506 (1988);
received February 17, 1988

The transformations occurring on annealing an as-spun amorphous $\text{Al}_{75}\text{Cu}_{15}\text{V}_{10}$ alloy are studied by X-ray diffraction and transmission electron microscopy (TEM). A continuous growth of icosahedral clusters, which are present already in the as-spun sample, is revealed. The size of the clusters estimated from the diffuse X-ray peak widths is consistent with the size of the modulation observed in the bright field TEM images.

Recently Chen et al. [1] reported a pronounced prepeak and a marked shoulder at the low Q -side of the main peak of the X-ray diffraction profile of amorphous $\text{Al}_{66}\text{Si}_{20}\text{Mn}_{14}$ and attributed these features to icosahedral short-range order clusters in the amorphous phase similar to those in α - $(\text{Al}_{77.5}\text{Si}_{10.1}\text{Mn}_{12.4})$ [2]. Extended X-ray absorption fine structure (EXAFS) measurements showed the similarity of the local atomic structure around a manganese atom in icosahedral and amorphous Al-Mn alloys [3]. Also quantitative analyses of X-ray diffraction profiles of amorphous sputtered $\text{Al}_{77.5}\text{Mn}_{22.5}$ and as-spun $\text{Al}_{56}\text{Si}_{30}\text{Mn}_{14}$ alloys confirmed the presence of icosahedral clusters resembling those in the α -phase [4]. The composition of the icosahedral and amorphous phases of aluminum alloys recently studied usually varied, and even for the same composition different sample preparation techniques were used. This includes the $\text{Al}_{86-x}\text{Si}_x\text{Mn}_{14}$ alloy [5].

On the other hand, the icosahedral phase has recently been found to form as a stable intermediate in Pd-U-Si [6] and Al-Cu-V [7] on annealing the amorphous phase at a temperature below the melting point. Tsai et al. [7] observed an exothermic reaction at 731 K in the differential scanning calorimetry (DSC) curve of amorphous $\text{Al}_{75}\text{Cu}_{15}\text{V}_{10}$ and interpreted it as the formation of the icosahedral phase. However, the structural features of this phase are not yet revealed. The present note provides some interesting results about these features.

A mixture of electrolytic Al, Cu, and V was melted under argon in an arc furnace, and from the alloy amorphous ribbons about 0.02 mm thick and 1 mm wide were prepared by a single roller melt spinning apparatus. Two samples were annealed under argon gas atmosphere for 40 800 sec and 86 400 sec, respectively, at 620 K. The icosahedral phase was

prepared by heating the amorphous sample for 300 sec at 820 K. X-ray scattering intensities from powder samples prepared by grinding the ribbons were measured with a molybdenum X-ray tube and a singly-bent pyrolytic graphite monochromator in a diffracted beam. At least 10 000 counts were collected at each scattering angle, so that the counting statistical error was smaller than 1%. Bright field (BF) images of the ribbons and their selected area diffraction patterns (SADP) were obtained by transmission electron microscopy (TEM).

Figure 1 shows BF electron micrographs and their SADPs of the annealed samples. For micrographs of the as-spun sample and the sample heated for 300 sec at 820 K, cf. [7]. The diffraction patterns of the annealed samples show a diffuse halo which proves that they are amorphous. Any macroscopic structural heterogeneity was not detected in the BF images, but they show a very fine modulated structure whose size is about a few nm. In the sample heated at 820 K, the grain size of the icosahedral phase was found to be about 0.7 μm , and its SADP shows the fivefold symmetric pattern of a typical icosahedral structure [7].

The X-ray diffraction profiles of the four samples are shown in Figure 2. As expected from the SADP, the diffraction profile of the as-spun sample indicates a non-crystalline structure. However, there are also some distinct features: a pronounced prepeak at $Q = 16 \text{ nm}^{-1}$, a shoulder on the low- Q side of the main peak and a small hump at $Q = 40 \text{ nm}^{-1}$. Similar features were observed for amorphous $\text{Al}_{66}\text{Si}_{20}\text{Mn}_{14}$ [1], $\text{Al}_{56}\text{Si}_{30}\text{Mn}_{14}$ [4], and $\text{Al}_{76}\text{Cu}_{14.5}\text{V}_7\text{Si}_{1.5}\text{Mo}_1$ [8]. In general, the prepeak corresponds to the so-called compound forming behavior in non-crystalline systems [9–11], and the prepeak in the amorphous Al-Si-Mn alloy has been interpreted by the presence of chemical short-range order of Mn-Mn pairs positioned at the vertices of the icosahedral clusters [4]. A similar shoulder as mentioned above was observed in as-spun amorphous $\text{Al}_{56}\text{Si}_{30}\text{Mn}_{14}$ [1] and sputtered amor-

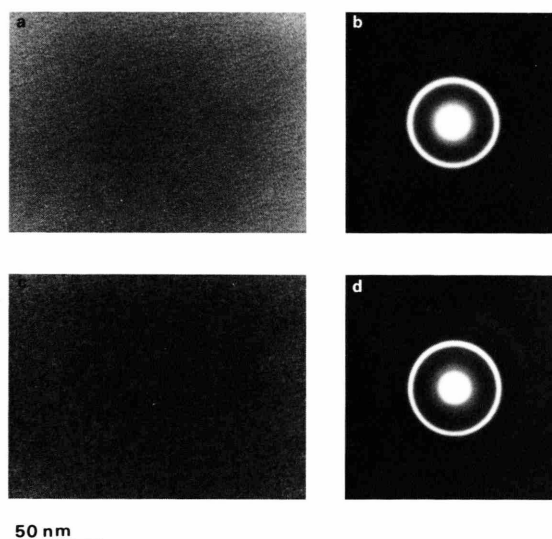


Fig. 1. Bright field electron micrographs (a, c), and selected area diffraction patterns (b, d) of an amorphous $\text{Al}_{75}\text{Cu}_{15}\text{V}_{10}$ alloy aged for 40 800 sec (a, b) and 86 400 sec (c, d) at 620 K.

Reprint requests to Dr. E. Matsubara, Research Institute of Mineral Dressing and Metallurgy (SENKEN), Tohoku University, Sendai 980, Japan.

0932-0784 / 88 / 0500-0505 \$ 01.30/0. – Please order a reprint rather than making your own copy.



Dieses Werk wurde im Jahr 2013 vom Verlag Zeitschrift für Naturforschung in Zusammenarbeit mit der Max-Planck-Gesellschaft zur Förderung der Wissenschaften e.V. digitalisiert und unter folgender Lizenz veröffentlicht: Creative Commons Namensnennung-Keine Bearbeitung 3.0 Deutschland Lizenz.

Zum 01.01.2015 ist eine Anpassung der Lizenzbedingungen (Entfall der Creative Commons Lizenzbedingung „Keine Bearbeitung“) beabsichtigt, um eine Nachnutzung auch im Rahmen zukünftiger wissenschaftlicher Nutzungsformen zu ermöglichen.

This work has been digitalized and published in 2013 by Verlag Zeitschrift für Naturforschung in cooperation with the Max Planck Society for the Advancement of Science under a Creative Commons Attribution-NoDerivs 3.0 Germany License.

On 01.01.2015 it is planned to change the License Conditions (the removal of the Creative Commons License condition “no derivative works”). This is to allow reuse in the area of future scientific usage.

