

---

Los Alamos National Laboratory is operated by the University of California for the United States Department of Energy under contract W-7405-ENG-36

---

TITLE: VAPORIZATION BEHAVIOR OF  $U_xZr_{1-x}C_{1-y}$  NUCLEAR FUEL MATERIALS  
IN HYDROGEN AT HIGH PRESSURES AND TEMPERATURES

AUTHOR(S): Darryl P. Butt and Edmund K. Storms  
NMT-1 Los Alamos National Laboratory  
Los Alamos, NM, U.S.A.

SUBMITTED TO NUCLEAR TECHNOLOGIES FOR SPACE EXPLORATION  
August 16-19, 1992  
Snow King Resort, Jackson Hole, Wyoming

### DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

By acceptance of this article the publisher recognizes that the U.S. Government retains a nonexclusive, royalty free license to publish or reproduce the published form of this contribution or to allow others to do so, for U.S. Government purposes.

The Los Alamos National Laboratory requests that the publisher identify this article as work performed under the auspices of the U.S. Department of Energy.

---

 **Los Alamos** Los Alamos National Laboratory  
Los Alamos, New Mexico 87545

MASTER

22

# Vaporization Behavior of $U_xZr_{1-x}C_{1-y}$ Nuclear Fuel Materials in Hydrogen at High Pressures and Temperatures

Darryl P. Butt and Edmund K. Storms  
Los Alamos National Laboratory, Los Alamos, NM, U.S.A.

The corrosion behavior of nuclear fuel materials, such as refractory carbides, in hydrogen gas is an important issue for a variety of space propulsion concepts. The rate of vaporization will limit the reactor life and must therefore be well understood. This paper describes the thermodynamics and kinetics of the vaporization of  $U_xZr_{1-x}C_{1-y}$  solid solutions in hydrogen gas; and it describes how vaporization rates are influenced by pressure, temperature, gas flow rate, dissociated hydrogen, and the addition of hydrocarbon to the hydrogen gas stream. It is demonstrated that a thermokinetic model agrees with hydrogen corrosion data at 1 atm between 2670 and 3100K. Comparison of experimental and calculated corrosion fluxes indicates that under these conditions the steady state corrosion of  $U_xZr_{1-x}C_{1-y}$  is rate limited by gaseous transport of Zr(g) from the solid surface to the bulk gas stream where the partial pressure of Zr(g) is controlled by the congruently vaporizing surface composition (CVC). Extrapolation of the model to higher pressures indicates that Zr(g) transport should also be rate limiting at higher pressures but the corrosion rate should decrease with increased total pressure due to reduced gaseous diffusion rates.\* This work extends a model previously described by Storms<sup>1</sup> which was based on experimental data in which he assumed an average vaporization coefficient and Langmuir vaporization. Storms also described the mechanism of formation of the CVC and its importance in determining corrosion rates.

## Calculations of Corrosion Rates

The corrosion rate of  $U_xZr_{1-x}C_{1-y}$  may be described using a flux equation, analogous to Fick's first law of diffusion, as follows:

$$J_{UZrC} = J_i = -\frac{h_i \Delta p_i}{RT} \quad (1)$$

where  $J_{UZrC}$  is the molar flux of  $U_xZr_{1-x}C_{1-y}$  away from the surface,  $J_i$  is the molar flux of the rate controlling gaseous product species,  $i$ , away from the surface,  $\Delta p_i$  is the change in the partial pressure of species  $i$  between the bulk gas stream and the CVC surface, and  $RT$  has its usual meaning. The average or effective mass transfer coefficient,  $h_i$  may be determined from boundary layer theory and, for the particular bullet-shaped geometry used in these studies may be expressed as:<sup>2</sup>

$$h_i = \frac{D_{ij}}{L} (0.70 R_c^{1/2} S_c^{1/3}) \quad (2)$$

where  $L$  is the characteristic dimension of the solid (bullet diameter),  $D_{ij}$  is the gaseous interdiffusion coefficient for species  $i$  through, in this case, hydrogen,  $R_c$  is the Reynolds number, and  $S_c$  is the Schmidt coefficient. The gaseous interdiffusion coefficient may be expressed as follows:<sup>3</sup>

\* Calculations suggest that corrosion rates could increase slightly at high pressures due to the formation of  $ZrH(g)$ . However, good thermodynamic data for this species do not exist.

$$D_{ij} = \frac{3kT}{8P} \sqrt{\frac{kT(m_i+m_j)}{2P m_i m_j}} \cdot \frac{1}{\sigma_{ij}^2 \Omega_D \left(\frac{kT}{\epsilon_{ij}}\right)} \quad (3)$$

where  $k$  is the Boltzmann's constant,  $P$  is total pressure, and  $m$  represents molecular mass. The terms  $\sigma_{ij}$  and  $\epsilon_{ij}$  are Lennard-Jones potential parameters and  $\Omega_D$  is referred to as the Lennard-Jones potential; Values of or methods for calculating these parameters are well documented.<sup>4,5</sup> The dimensionless terms  $R_c$  and  $S_c$  in (2) may be calculated from the following relationships:

$$R_c = \frac{Lv}{\nu} \quad (4)$$

and

$$S_c = \frac{v}{D_{i-mix}} \quad (5)$$

where  $v$  is the bulk gas stream velocity and  $\nu$  is the kinematic viscosity.

Equation (1) was used to calculate the corrosion rate of  $U_xZr_{1-x}C_{1-y}$  in hydrogen at 1 atm between 2500 and 3200K. The values for  $\Delta p_i$  were obtained by calculating the partial pressures above the CVC using thermodynamic data from several sources.<sup>6-9</sup> In a fast flowing gas stream  $\Delta p_i \approx p_i$  where  $p_i$  is the equilibrium partial pressure of the rate limiting gaseous species. Thus the values of  $\Delta p_i$  used in calculating the corrosion fluxes corresponded to the equilibrium partial pressures of the most stable gaseous products, for example,  $U(g)$ ,  $Zr(g)$ ,  $C_2H_2(g)$ , and possibly  $ZrH(g)$ . Because it is well known that solid solutions of UC and ZrC deviate only slightly from Vegard's law, the  $U_xZr_{1-x}C_{1-y}$  solid solutions were assumed to be ideal solutions of UC and  $ZrC_x$  where thermodynamic data for  $ZrC_x$  were determined from activity measurements.<sup>9</sup>

#### Comparison of Calculated and Experimental Corrosion Rates and Extrapolations

Calculated corrosion rates were compared to hydrogen corrosion data from studies performed at Los Alamos National Laboratory which yielded the following Arrhenius relationship for  $U_{0.05}Zr_{0.95}C_{1.07}$  in 1 atm of hydrogen at 2670-3190K at a Reynolds number of approximately 500:<sup>10</sup>

$$\ln \text{rate}(\text{g}/\text{cm}^2\text{-sec}) = 10.891 - \frac{68618}{T} \quad (6)$$

Figure 1 shows a comparison of calculated versus experimental corrosion rates. The calculated data shown in figure 1 are based on two different assumptions: (1)  $Zr(g)$  transport from the CVC was rate limiting, and (2)  $C_2H_2(g)$  transport from the CVC was rate limiting. The relatively good agreement between the experimental data and assumption (1) above suggests that the corrosion of  $U_xZr_{1-x}C_{1-y}$  in hydrogen may be rate limited or partially rate limited by gaseous transport of  $Zr(g)$  from the surface.

The model was used to extrapolate to higher pressures as shown in figure 2. Throughout the pressure range shown, the corrosion rate is predicted to be controlled by the rate at which  $Zr(g)$  can diffuse through the gaseous boundary layer. Based on these calculations, it is expected that there will be a slight decrease in the corrosion rate as the pressure is increased due to the decreased gaseous diffusion rate of  $Zr(g)$ . Note also that at

very high pressures liquid is predicted to form on the surface due to the shift in the CVC. Details of the effects of gas flow rate, added hydrocarbon, and the presence of dissociated hydrogen will be discussed in the presentation and full paper.

### References

1. E.K. Storms, "The Behavior of  $ZrC_{1-x}$  and  $U_yZr_{1-y}C_{1-x}$  in Flowing Hydrogen at Very High Temperatures," LA-12043-MS, 1991.
2. W.M. Rohsenow and H. Choi, Heat, Mass, and Momentum Transfer, Prentice-Hall, Inc. 1961.
3. D.E. Rosner, Transport Processes in Chemically Reacting Flow Systems, Butterworths, Boston, 1986.
4. J.O. Hirschfelder, C.F. Curtiss, and R.B. Bird, Molecular Theory of Gases and Liquids, John Wiley & Sons, NY, 1954.
5. R.A. Svehla, "Estimated Viscosities and Thermal Conductivities of Gases at High Temperatures," NASA TR R-132, 1962.
6. JANAF Thermochemical Tables, 3rd Ed., M.W. Chase, Jr., C.A. Davies, J.R. Downey, Jr., D.J. Frurip, R.A. McDonald, and A.N. Syverud, Editors, Am. Chem. Soc. and the Am. Institute of Phys. for the NBS, Vol. 14, 1985.
7. Private communications with M.W. Chase, Jr.: corrections to erroneous data for  $C_2H_2(g)$  in reference 6.
8. C.E. Holley, Jr., M.H. Rand, E.K. Storms, Editors, The Chemical Thermodynamics of Actinide Elements and Compounds, Part 6, The Actinide Carbides, International Atomic Energy Agency, Vienna, 1984.
9. E.K. Storms and J. Griffin, "Thermodynamic and Phase Relationships of the Zirconium-Uranium-Carbon System," *High Temp. Sci.*, Vol. 5, 423-437 (1973).
10. E.K. Storms, D. Hanson, W. Kirk, and P. Goldman, "Effect of Fuel Geometry on the Life Time-Temperature Performance of Advanced Nuclear Propulsion Reactors," Proceedings of the AIAA/NASA/OAI Conference on Advanced SEI Technologies, AIAA 91-3454, 1991.

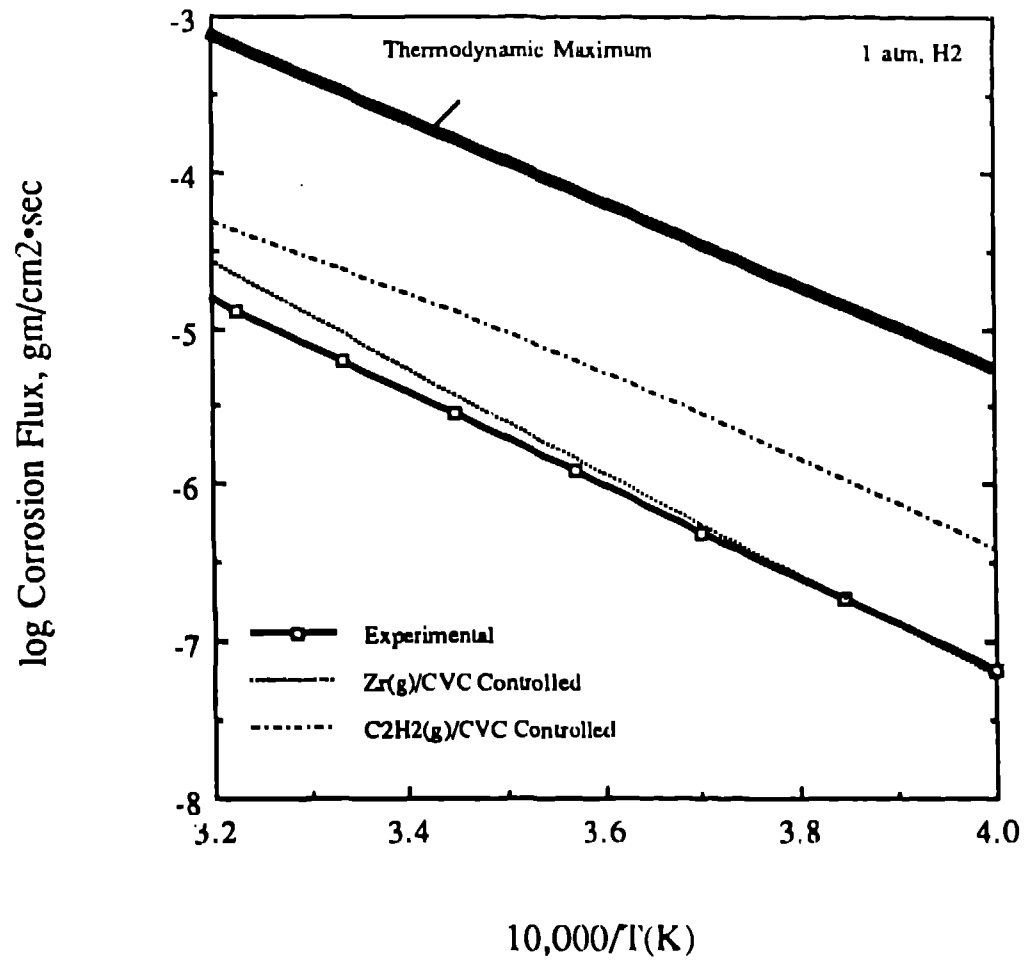


Figure 1. Arrhenius plot of corrosion flux comparing measured and calculated rates.

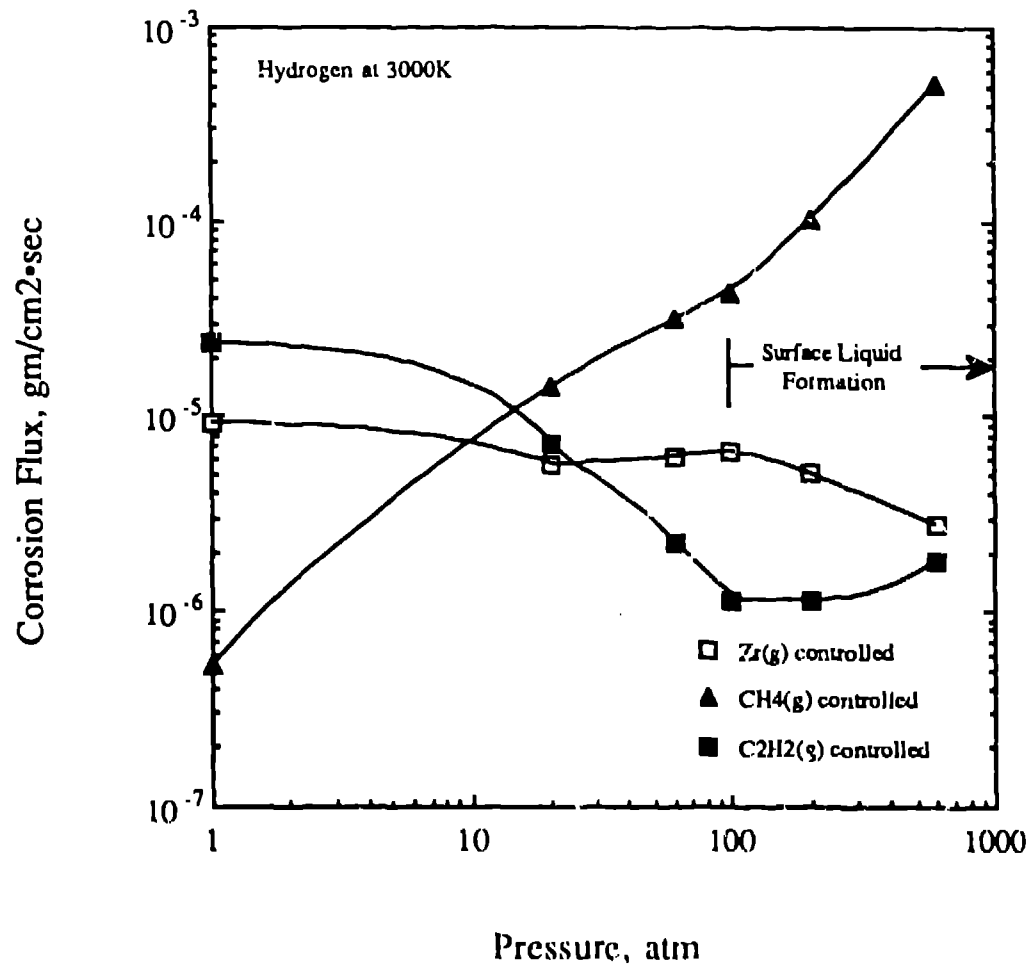


Figure 2. Calculated corrosion flux versus hydrogen pressure under three assumptions: that corrosion is rate limited by the gaseous transport of Zr, CH<sub>4</sub>, and C<sub>2</sub>H<sub>2</sub>.