

Remarks on Recent Measurements of the Paramagnetic Effect in Tin*

HANS MEISSNER

Department of Physics, Johns Hopkins University, Baltimore, Maryland

(Received March 15, 1956)

It is shown that the measurements of Shibuya and Tanuma substantiate rather than invalidate the statement that the maximum permeability in the paramagnetic effect occurs for given values of the current I and the external field H at a temperature where the total magnetic field at the surface of the sample is equal to the critical field. It is further shown that their new equations, $I_0 = \xi\gamma^*d(T_c - T)/4$ and $H_0 = \xi(T_c - T) - 4I_0/\gamma^*d$, follow as a first approximation from the statement that the maximum permeability depends only on $\gamma = 4(I - I_0)/Hd$.

SHIBUYA and Tanuma have recently reported some measurements of the paramagnetic effect in tin.^{1,2} The authors claim that their measurements are inconsistent with statements brought forth earlier.³ These statements were:

1. The maximum apparent permeability μ^* (denoted by \tilde{K}_m in reference 3) occurs for a given current, I and external field, H , at a temperature where the total magnetic field H_t at the surface of the sample equals the critical field H_c : $H_t = [H^2 + (4I/d)^2]^{1/2} = H_c(T)$, where H is measured in oersteds, I in amperes, and the diameter d of the sample in mm.
2. The maximum apparent permeability is a function of $\gamma = 4(I - I_0)/Hd$.

Our γ is dimensionless and considered as a variable. I_0 is a constant characteristic of the metal. The exact dependence of μ^* on γ may vary to some extent from sample to sample. For values of $1 \leq \mu^* \leq 2$ this dependence can be approximated by $\mu^* - 1 = \alpha(\gamma - \gamma^*)$, where γ^* is another constant, which is probably also characteristic for each metal. It has a value which is numerically four times greater than that of the constant γ (later denoted by γ_{S-T}) which Shibuya and Tanuma use.

Shibuya and Tanuma claim that the maximum permeability occurred in all their measurements at values of $H_t < H_c$. They try to prove this in Fig. 18 of reference 1, which shows a plot of I versus H with μ as parameter for a temperature of $T = 3.590^\circ\text{K}$. Instead of basing the argument on the measurements at one temperature only, we have calculated H_t for all their measurements of μ^* on sample 1 and plotted H_t versus T in Fig. 1. It is true that most of their measurements lie below the curve $H_t = 138(T_c - T)$ which the authors claim to be the correct $H_c - T$ relationship near T_c . But the value of $(dH_c/dT)_{T_c}$ varies to some extent from sample to sample. Lock, Pippard, and Shoenberg⁴ report that $(dH_c/dT)_{T_c} = -152$ oersteds per degree.

We find that most of the measurements of Shibuya and Tanuma are on the curve $H_c = 130(T_c - T)$. Some measurements, however, are made with T and I fixed such that already $(4I/d) > H_c$. For all values of $H < H_c$ the sample consists in these cases of an intermediate core surrounded by a normal conducting sheath. (This does not prevent μ from going through a pseudomaximum if H is varied.) It has been shown⁵ that one can calculate the over-all μ for these cases quite accurately. We will, however, refrain here from going into these calculations and disregard those points. The slight scattering which remains in the $H_c - T$ values, even after adjustment of the slope and subtraction of the points for which already $(4I/d) > H_c$, is probably due to slight variations in the temperature. It is to be noted that a deviation

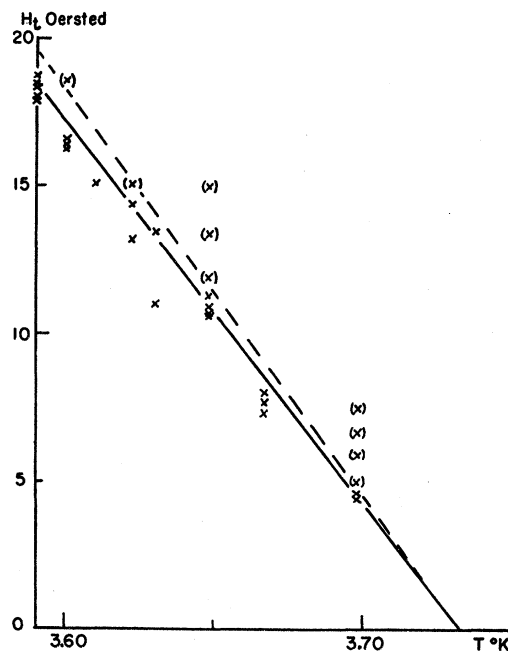


FIG. 1. Total magnetic field H_t at the surface of the sample as a function of the temperature T as calculated from Shibuya and Tanuma's measurements of the maximum permeability μ^* on their sample No. 1. The points enclosed in parentheses (\times) are taken at values where $(4I/d) > H_c$. Broken curve: $H_c = 138(T_c - T)$; solid curve: $H_c = 130(T_c - T)$.

* Supported by a grant of the National Science Foundation.

¹ Y. Shibuya and S. Tanuma, Sci. Repts. Research Inst. Tohoku Univ. A7, 549 (1955).

² Y. Shibuya and S. Tanuma, Phys. Rev. 98, 938 (1955).

³ Hans Meissner, Phys. Rev. 97, 1627 (1955).

⁴ Lock, Pippard, and Shoenberg, Proc. Cambridge Phil. Soc. 47, 811 (1951).

⁵ Hans Meissner, Phys. Rev. 101, 31 (1956).

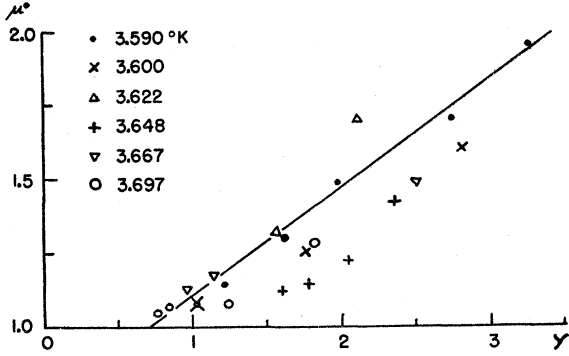


FIG. 2. Maximum permeability μ^* as a function of $\gamma = 4(I - I_0)/Hd$, as calculated from Shibuya and Tanuma's measurements on their sample No. 1. All the points for which $(4I/d) > H_c$ have been omitted. Solid curve: $\mu^* - 1 = \alpha(\gamma - \gamma^*)$, with $\gamma^* = 0.7$.

tion of 1 oersted corresponds to only 0.0072°K . It is therefore believed that the measurements of Shibuya and Tanuma substantiate rather than invalidate our first statement.

We have further calculated γ from their measurements and plotted μ^* as a function of γ in Fig. 2, omitting all measurements where $(4I/d) > H_c$. There is a considerable scattering around the curve $\mu^* - 1 = \alpha(\gamma - \gamma^*)$. This scattering, however, is typical for all measurements of the paramagnetic effect and increases with a decrease in sample size. We believe, therefore, that $\mu^* - 1 = \alpha(\gamma - \gamma^*)$ is a valid approximation in spite of the scattering.

We want now to demonstrate that the functional relationships shown in Figs. 8, 10, 12, and 13 of reference 1 and expressed in Eqs. (2) and (3) of reference 1 can be explained by using our two statements, the equation $\mu^* - 1 = \alpha(\gamma - \gamma^*)$ and the relation between H_c and T .

In their Fig. 8 Shibuya and Tanuma plot μ^* as function of I with T as parameter. $T = \text{const}$ means $H_c = \text{const}$ and we find that the equation $\mu^* - 1 = \alpha(\gamma - \gamma^*)$ has for this case the form

$$\mu^* - 1 = \alpha \left(\frac{4(I - I_0)}{d[H_c^2 - (4I/d)^2]} - \gamma^* \right). \quad (1)$$

This equation represents the general trend of the measurements fairly well as long as $(4I/d) < H_c$. μ^* is larger than one as long as $I > I_0$, where I_0 is the value of I which makes the right side of Eq. (1) vanish. I_0 is the solution of a quadratic equation containing H_c , I_0 , d , and γ^* . Since most of the measurements of I_0 are made in a region where $(H_c d / 4I_0) \gg 1$ (see Fig. 12 of

reference 1) we can write in first approximation

$$I_0 = \frac{\gamma^* H_c d}{4(1 + \gamma^{*2})^{1/2}} = - \frac{dH_c/dT}{(1 + \gamma^{*2})^{1/2}} \frac{\gamma^* d}{4} (T_c - T). \quad (2)$$

Observing that our $\gamma^* = 4\gamma_{S-T}$, we find by comparison of Eq. (2) with Eq. (2) of reference 1 that the constant ξ introduced by Shibuya and Tanuma is given by $\xi = -(1 + \gamma^{*2})^{-1/2} (dH_c/dT)$. This gives with $dH_c/dT = -130$ and $\gamma^* = 0.7$ a value of $\xi = 107$ oersted per degree as compared to their value of $\xi = 112$ oersted per degree.

We can, on the other hand, also express μ^* as a function of H^* with T as parameter (fixed H_c). H^* is the value of H which, for a given $I < H_c d / 4$, makes $H_t = H_c$. We find, as in Eq. (1), that

$$\mu^* - 1 = \alpha \left(\frac{[H_c^2 - H^{*2}]^{1/2} - 4I_0/d}{H^*} - \gamma^* \right). \quad (3)$$

This represents again the general trend of the curves in Fig. 10 of reference 1 fairly well as long as $I < H_c d / 4$. μ^* is larger than one if $H^* < H_0$, where H_0 is the value of H^* which makes the right side of Eq. (3) vanish. H_0 is readily found as the solution of a quadratic equation containing H_c , I_0 , d , and γ^* . For values of $H_c \gg 4I_0/d$, this equation can be greatly simplified. Observing that $\gamma^* = 4\gamma_{S-T}$ and $\xi = -(1 + \gamma^{*2})^{-1/2} (dH_c/dT)$ we find finally

$$H_0 = \xi(T - T_c) - \frac{I_0}{\gamma_{S-T} d} \frac{\gamma^{*2}}{1 + \gamma^{*2}}. \quad (4)$$

Equation (4) differs from Eq. (3) of reference 1 by a factor $\gamma^{*2}/(1 + \gamma^{*2}) = 0.3$ in the second (constant) term. Figure 13 of reference 1 shows, moreover, that the measured points can be fitted much better by a quadratic equation and that the simplification which was used in the derivation of Eq. (4) actually should not be applied. One finds readily from the correct solution for H_0 that the constant T_g which Tanuma and Shibuya use is the temperature at which $H_c = 4I_0/d$, i.e., $T_g = T_c + (4I_0/d)(dH_c/dT)^{-1}$.

It should further be noted that the authors use γ_{S-T} in Eqs. (2) and (3) of reference 1 as a dimensionless quantity, but in Eq. (4) of reference 1 they use it as a constant of the dimension ampere/millimeter oersted. The numerical value which they use is that of the constant with dimension, while the dimensionless quantity is four times larger.

The author wants to thank the National Science Foundation for supporting this work by a grant.