

FIG. 1(a). Calculated anisotropy constant, K_1 , (b) observed average magnetostriction constant, λ_s , plotted against M , for the ferromagnetic spinels, $M\text{Fe}_2\text{O}_4$. Below each M is the ground-state term of M^{++} .

cooled slowly and are presumably nearly strain-free, with the exception of CuFe_2O_4 which had to be quenched. Values of M_s at room temperature were obtained in these laboratories and from other appropriate sources.⁹

The calculated values of $|K_1|$ for $M\text{Fe}_2\text{O}_4$ are plotted in Fig. 1(a) versus the ground-state term of M^{++} . One will note there the direct correspondence between K_1 and J , the inner quantum number of M^{++} . Such a relationship is expected in view of the dependence of magnetic anisotropy on spin-orbit coupling. Van Vleck¹⁰ has discussed a similar behavior in the paramagnetic bivalent salts of the iron series.

We find by our calculations, $K_1 = -4.0 \times 10^4$ ergs/cm³ for NiFe_2O_4 and $K_1 = -3.4 \times 10^6$ for CoFe_2O_4 . Experimental values are, respectively,^{11,1} -5.1×10^4 and -1.7×10^6 . Since these experimental values were obtained on crystals containing some magnetite in solid-solution,¹ it seems reasonable that K_1 for NiFe_2O_4 is higher and K_1 for CoFe_2O_4 , lower, respectively than what we calculated for pure materials.

Figure 1(b) is a plot of $|\lambda_s|$, the average value of the saturation magnetostriction for sintered, polycrystalline

ferromagnetic spinels. (We have ignored the fact that λ_s is positive for Fe_3O_4 and negative for the others). The values for λ_s were obtained here (with the exception of CoFe_2O_4)¹² and are believed to be accurate to ± 25 percent. One will note again the same type of dependence on J .

- ¹ R. M. Bozorth and J. G. Walker, Phys. Rev. **88**, 1209 (1952).
- ² J. Smiltens, J. Chem. Phys. **20**, 990 (1952).
- ³ L. R. Bickford, Jr., Phys. Rev. **78**, 449 (1950).
- ⁴ H. Danan, Compt. rend. **238**, 1304 (1954).
- ⁵ J. J. Went and H. P. J. Wijn, Phys. Rev. **82**, 269 (1951); see also F. Brown and C. Gravel, Phys. Rev. **95**, 652 (1954).
- ⁶ R. M. Bozorth, *Ferromagnetism* (D. Van Nostrand Company, Inc., New York, 1951), pp. 821-2.
- ⁷ C. Kittel, J. phys. et radium **12**, 291 (1951).
- ⁸ H. P. J. Wijn, dissertation, Leiden, 1953 (unpublished), p. 37.
- ⁹ R. Pauthenet and L. Bochirol, J. phys. et radium **12**, 249 (1951); references to earlier work may be found here.
- ¹⁰ J. H. Van Vleck, Phys. Rev. **41**, 208 (1932).
- ¹¹ D. W. Healy, Jr., Phys. Rev. **86**, 1009 (1952).
- ¹² R. Vautier, Compt. rend. **235**, 356 (1952).

Infrared Spectrum of Barium Titanate*

R. T. MARA, G. B. B. M. SUTHERLAND, AND H. V. TYRELL
Randall Physics Laboratory, University of Michigan,
Ann Arbor, Michigan

(Received September 16, 1954)

THE infrared absorption of barium titanate (BaTiO_3) has been studied between 2μ and 33μ . The spectrum obtained (Fig. 1) consists of two broad bands, one centered near 550 cm^{-1} , the other starting near 450 cm^{-1} and reaching a maximum beyond 300 cm^{-1} . The low transmission in the high-frequency end of the spectrum is due to scattering since the barium titanate was examined as a fine powder deposited on a KBr (or NaCl) plate from a suspension in isopropyl alcohol.

Several specimens of barium titanate were examined. The majority showed additional bands at 6.95 , 9.45 , and 11.65μ , which were proved to be due to carbonate ion impurities. Other impurity bands were noted at 7.1 , 10.3 , 11.05 , 11.4 , 11.85 , and 12.85μ , but the impurities were not identified. The spectrum of a very

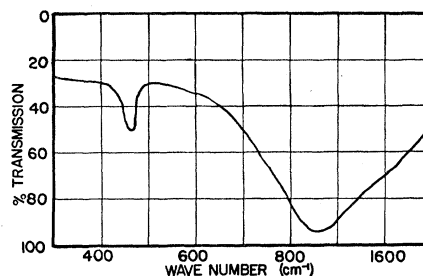


FIG. 1. The infrared absorption spectrum of BaTiO_3 .

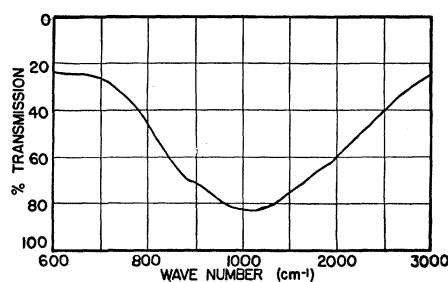


FIG. 2. The infrared absorption spectrum of SrTiO_3 .

pure specimen of powdered strontium titanate (SrTiO_3) was observed between 2μ and 15μ (Fig. 2). It is identical with that of barium titanate obtained under similar conditions over that region of the spectrum. Noland¹ has recently reported the spectrum of a single crystal of strontium titanate between 1μ and 10.5μ , at which wavelength the extinction coefficient is greater than 100 cm^{-1} and is still increasing. He finds two weak bands near 5.5μ and 7.5μ . These could easily have been missed by us since our effective thickness was much less than the thickness he used. We might add that the spectrum of a single crystal of barium titanate just run in this laboratory by M. Haas shows a weak band at 8μ and a "cutoff" near 11.2μ . The spectrum of ilmenite (FeTiO_3) has been recorded by Hunt and others.² With the exception of a weak band at 1000 cm^{-1} , it is also very similar to that of barium titanate.

Apart from impurity bands, there appears to be no difference between the spectrum of barium titanate in the hexagonal and in the tetragonal form over the range 2μ to 15μ . No change was observed in the spectrum of barium titanate (ceramic) when heated to 150°C .

The foregoing observations may be considered in the light of recent theories about the ferroelectric character of barium titanate.

Jaynes³ has predicted from an electronic theory that there should be an infrared absorption at 1000 cm^{-1} . There is definitely no *strong* absorption band in the neighborhood of 1000 cm^{-1} . Although a few specimens have shown a very weak absorption near 1000 cm^{-1} , this is most probably due to BaO impurity.

Megaw⁴ has proposed that the change from the cubic form (above the Curie point of 120°C) to the tetragonal form corresponds to a change in the character of the bonds round the Ti and O atoms. If this were so, one might expect a change in the spectrum on heating to 150°C and also differences between the spectra of the tetragonal and hexagonal forms of BaTiO_3 since the latter is not ferroelectric. This change should be very marked in the strong band near 600 cm^{-1} since this band [which is common to all titanates and is found also in rutile (TiO_2)] is undoubtedly connected with a vibration of the TiO_4 tetrahedra. No such change was ob-

served. It is possible, of course, that changes may have occurred at lower frequencies beyond our range of detection.

* This work was sponsored by the Signal Corps. Engineering Laboratory.

¹ J. A. Noland, Phys. Rev. **94**, 724 (1954).

² Hunt, Wisherd, and Bonham, Anal. Chem. **22**, 1478 (1950).

³ E. T. Jaynes, *Ferroelectricity* (Princeton University Press, Princeton, 1953), p. 69.

⁴ H. D. Megaw, Acta Cryst. **5**, 739 (1952).

Hyperfine Splitting of Donor States in Silicon

J. M. LUTTINGER* AND W. KOHN†

Bell Telephone Laboratories, Murray Hill, New Jersey

(Received September 3, 1954)

ELECTRON spin resonances exhibiting hyperfine structure have recently been observed in *n*-type Si by Fletcher *et al.*¹ The number of hyperfine lines of these resonances corresponds exactly to the nuclear spin of the added Group V atoms, showing conclusively that the resonances are due to electrons localized near such atoms. It has therefore been assumed¹ that the resonances arise from the well-known donor states with ionization energies of about 0.04 to 0.05 eV. We have made a theoretical estimate of the hyperfine splitting of phosphorus donor states to be expected on this assumption and find agreement with experiment within a factor of ~ 2.5 . (We estimate the uncertainty of our theoretical result as about a factor of 5.)

Following is a brief summary of our calculations; a detailed report will be published shortly. The conduction band of Si has 6 minima on the (1,0,0) and equivalent axes.² The effective masses at one of these minima are $0.19m$ (twice) and $0.99m$.³ Let $\psi(\mathbf{k}^{(i)}, \mathbf{r})$ be the Bloch function corresponding to the energy minimum at $\mathbf{k}^{(i)}$, so normalized that

$$\int_{\text{cell}} |\psi(\mathbf{k}^{(i)}, \mathbf{r})|^2 d\tau = \text{volume of unit cell}, \quad (1)$$

and phased so as to be real at $\mathbf{r}=0$. It may then be shown that in the so-called effective mass approximation, the normalized ground-state wave function of the donor electron has the following form:

$$\psi(\mathbf{r}) = \frac{1}{(6)^{\frac{1}{2}}} \sum_{i=1}^6 F^{(i)}(\mathbf{r}) \psi(\mathbf{k}^{(i)}, \mathbf{r}). \quad (2)$$

The $F^{(i)}(\mathbf{r})$ satisfy effective mass equations with the above masses and the potential $-e^2/\kappa r$ (κ =dielectric constant). They are taken as real and are normalized to unity over all space. The hyperfine splitting is then determined by the value of

$$|\psi(0)|^2 = 6 |F^{(1)}(0)|^2 |\psi(\mathbf{k}^{(1)}, 0)|^2. \quad (3)$$